

**PIXE Spectroscopy for Determination
of Volatile Corrosion Inhibitor Concentration
in Anticorrosion Polymer Films**

Irina Pucić
Milko Jakšić
Ruđer Bošković Institute
Zagreb, Croatia

Tadija Madžar
Military of Defense
Republic of Croatia
Zagreb, Croatia

Ivan Rogan
Cortecros Co. Ltd.
Zagreb, Croatia

Abstract

Anti-corrosion polymer films used from 0 to 6 years were investigated to determine the type and content of volatile corrosion inhibitors (VCI) and how long the films emit them to protect the metal surface encased in the film. Using FTIR and DSC low density polyethylene (LDPE) was identified as the polymer carrier. Particle induced X-ray emission (PIXE) spectroscopy of anti-corrosion polymer films revealed significant concentration of molybdenum (Mo) implying that corrosion inhibitor composition was molybdate based. The films were divided into three groups according to different rates of VCI concentration decreasing with increasing age. The division of films into groups and diffusion of VCI was confirmed by significant decrease of Mo content determined by PIXE spectroscopy after accelerated aging in vacuum at 50 ° C. It was concluded that films with initial concentration of Mo above 6000 ppm emit VCI for at least 6 years while the films with less than 4000 ppm of molybdenum do not emit the VCI in ambient conditions.

Keywords. IR spectroscopy; DSC; Diffusion; Molybdate; LDPE.

Copyright

©2008 by NACE International. Requests for permission to publish this manuscript in any form, in part or in whole must be in writing to NACE International, Copyright Division, 1440 South creek Drive, Houston, Texas 777084. The material presented and the views expressed in this paper are solely those of the author(s) and are not necessarily endorsed by the Association. Printed in the U.S.A.

Introduction

Volatile corrosion inhibitors (VCI) or vapor phase corrosion inhibitors (VpCI) are chemical substances that, by evaporation from fluid or solid, create a monomolecular film on metal surface. Such film offers temporary corrosion protection, can easily be removed prior to the use of the metal item or even left untouched what is particularly beneficial in case of military equipment. One of the most important factors determining the efficiency of the VCI is its vapor pressure [1, 2] that has to be high enough to ensure the adequate VCI concentration to enable formation of the protective film on the metal surface and prevent corrosion. The vapor pressure is, among other factors, influenced by the form of VCI carrier. VCIs can be applied in number of forms such as powder, pellets, solutions in solvents or oils and, as in this case, can be coextruded in a polyolefinic film. Due to the simplicity of its application, such anti-corrosion polyolefinic films are being increasingly used in corrosion protection, from packaging of electronic products to protection of firearms of all sizes [1].

The anti-corrosion polymer films emit the VCI over a period of time thereby protecting the items encased by the film. To determine how long the films provide protection the first and very important step was to identify the VCI and determine its concentration and the rate of its evaporation, which was the goal of the presented investigation. In a further step the least concentration of VCI still providing anticorrosion protection should be determined what will be objective of further research.

As a nondestructive method that at the same time provides qualitative and quantitative information about the sample, particle induced X-ray emission (PIXE) spectroscopy was chosen. It belongs to ion beam techniques because the sample is exposed to the ion beam of MeV energy range inducing different atomic and nuclear processes that lead to the emission of products. Each product carries information about the sample composition, or some other material property (Figure 1).

When a charged particle (proton or heavier ion) enters the material, it encounters numerous inelastic collisions by sample atoms. From some of those numerous ionized atoms along the particle path, characteristic X-rays are emitted with a probability given by the X-ray production cross section. Advantages of PIXE spectroscopy stem from very high probability of X-ray emission – for most elements and sample types detection limits are of the order of 1 ppm, while simple X-ray spectra obtained by high energy resolution detectors make PIXE multielemental. Since the X-ray fluorescence yield and detector efficiency are lower for light elements, PIXE is most often used for the analysis of elements $11 < Z < 92$ so it can be employed for investigations of polymers or polymer containing samples. Some recent examples of application of PIXE to polymers follow. The diffusion of Se of CuInSe_2 absorber layers deposited into polyimide carrier foils of solar cells was detected by depth profiling with micro-PIXE method [3]. Diffusion of mono- and bi-functional monomers during and after photo-polymerization of acrylate based polymer gratings was monitored by PIXE and PIGE (particle induced γ -ray spectroscopy) [4, 5], and results were correlated to reactivity of monomers. Tadić et al. [6] measured distribution of Li, F, S, and Mn in gel-polymer, Li anode, and on the interfaces of gel-polymer, components of Li-ion battery, while Moretto et al. [7] analyzed terthiophene porphyrin conducting polymers and found trapped cations and traces of water from the electrolyte in which the polymer was synthesized. Based on such evidence, PIXE was chosen as a particularly convenient method that could be applied for qualitative as well as for quantitative analysis of VCI anticorrosion polymer films. Prior to that, identification of polymer carrier was performed by infrared spectroscopy and differential scanning calorimetry.

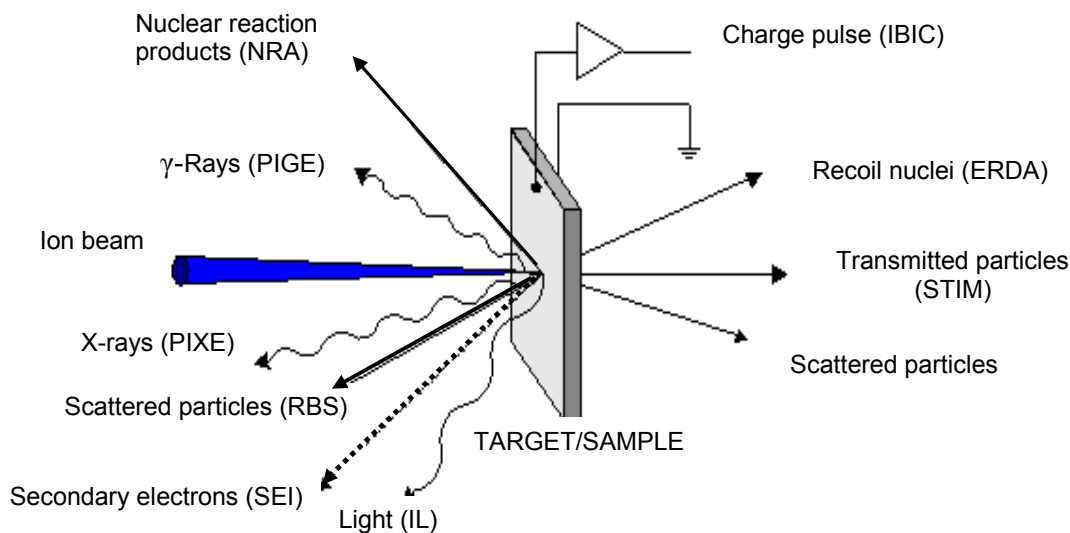


FIGURE 1 - The principles of ion beam analysis techniques

Experimental

Fourteen samples of new and used anti-corrosion films of age between 0 and 7 years were analyzed. The samples were marked by the year of their application (first 4 numbers) and a number from 0 to 2 was added for multiple samples in a corresponding year. The samples were kept sealed at room temperature. Accelerated aging of anti-corrosion films was performed in vacuum at 50° C for 223 days.

FTIR spectra of anti-corrosion films were taken on Bruker Tensor 27 with air as background, at room temperature.

DSC thermograms were recorded on Perkin Elmer DSC 7, in aluminum sample pans in nitrogen atmosphere. The temperature range was 0 to 200 ° C, scanning rate was 20 ° C / min, and two heating and cooling cycles were recorded for each sample.

For recording of PIXE spectra anti-corrosion film samples were put into the vacuum chamber in which 3 MeV protons coming out of a 6 MV Tandem Van de Graaff accelerator induced X-ray emission that was detected by X-ray Silicon Drift Detector.

Results and Discussion

The Analysis of Polymer Carrier of the Anti-Corrosion Films

All the investigated anti-corrosion polymer films had the same FTIR spectrum shown in Figure 2; Figures 3, 4, 5, and 6 show FTIR spectrum by year aging of anti-corrosion polymer films. The prominent absorptions at around 2900 cm^{-1} , out of the absorption range of the instrument because of film thickness, and absorptions at 1466 and 729 cm^{-1} indicate that the films are polyolefinic [8]. To identify the polyolefine, differential scanning calorimetry measurements on all anti-corrosion films were performed.

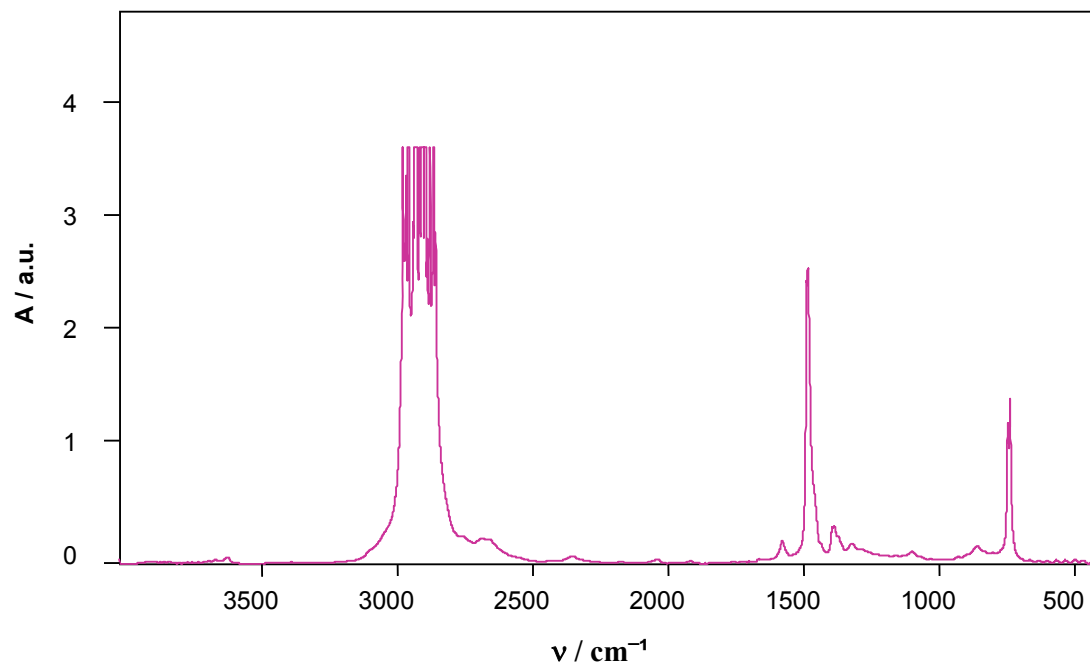


FIGURE 2 - FTIR spectra of analyzed anti-corrosion films

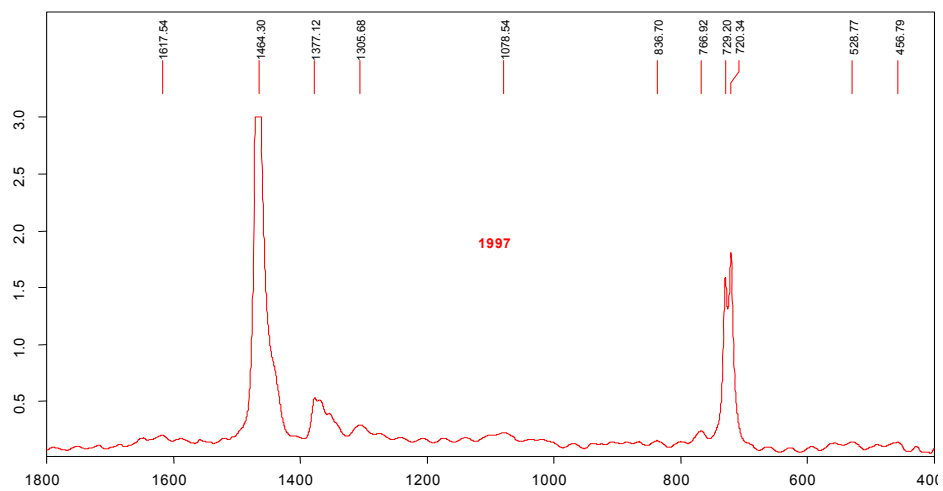


FIGURE 3 - FTIR spectra of analyzed anti-corrosion films, year 1997

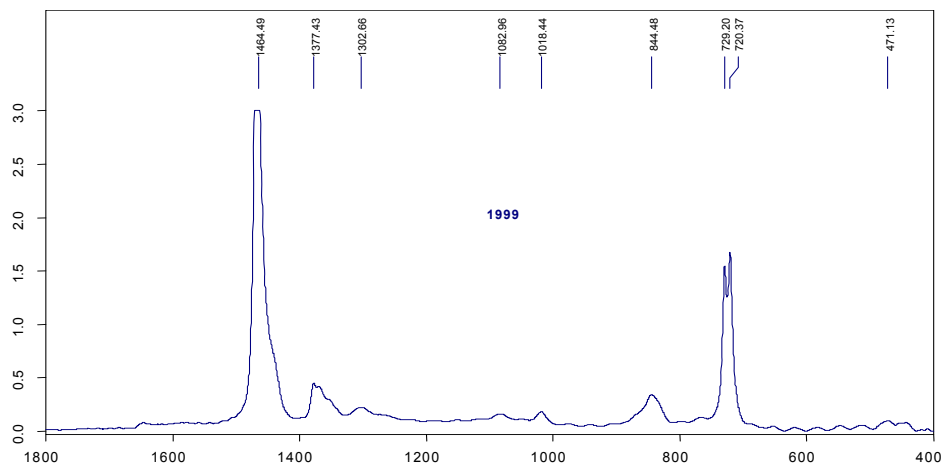


FIGURE 4 - FTIR spectra of analyzed anti-corrosion films, year 1999

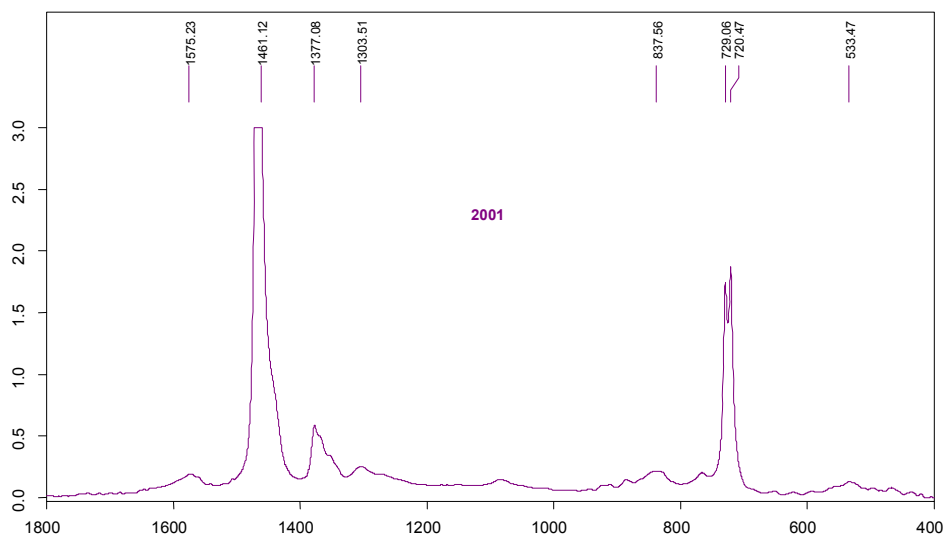


FIGURE 5 - FTIR spectra of analyzed anti-corrosion films, year 2001

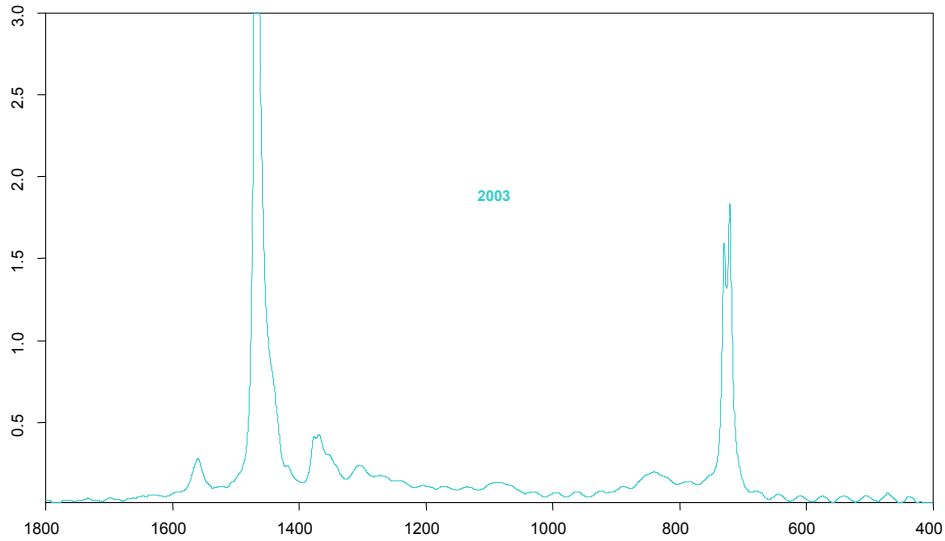


FIGURE 6 - FTIR spectra of analyzed anti-corrosion films, year 2003

The DSC thermograms had several characteristic patterns shown in Figure 7, that are denoted so the thermogram type could be identified in Table 1 where the temperatures and total heats of melting are listed. In all cases an endothermic process between 100° and 120° C was present, which is the temperature range of low density polyethylene (LDPE) (crystallite) melting point [9]. The onset of the melting process was just above 60° C what was important for setting the conditions for accelerated ageing of anti-corrosion films. No other processes at higher temperature were detected and taking into account the FTIR spectra, the polymer carrier of the anti-corrosive films was identified as LDPE.

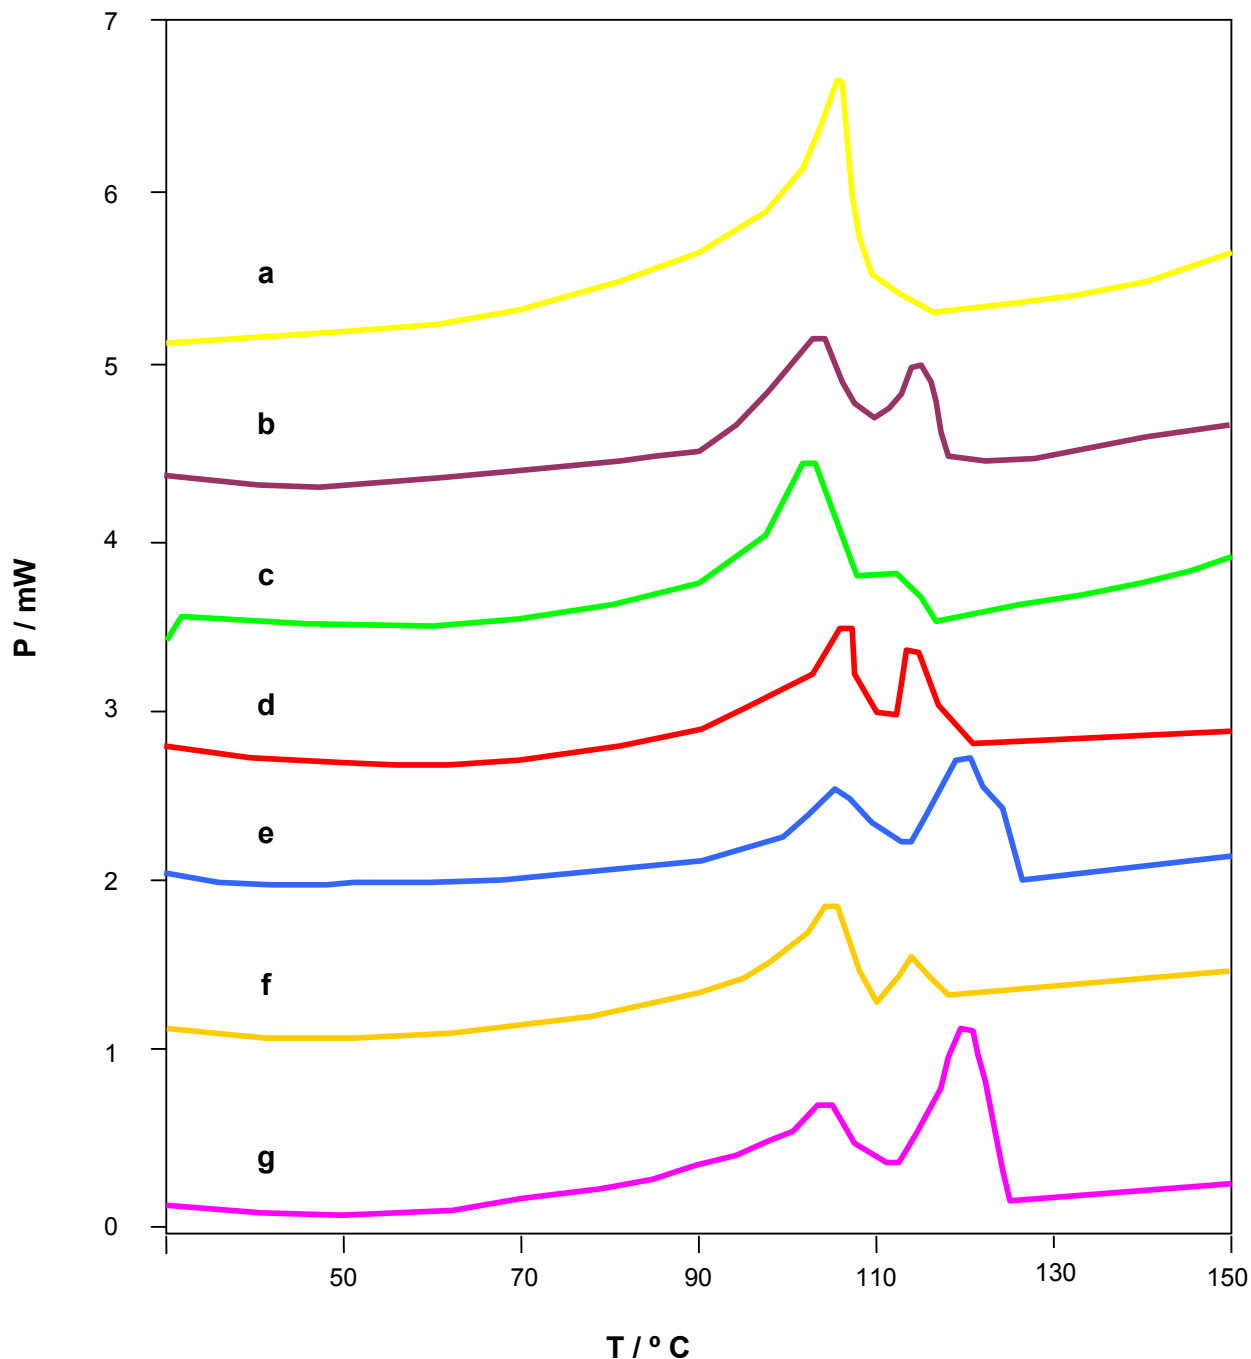


FIGURE 7 - Typical DSC thermograms of analyzed anti-corrosion films

In most cases the melting process was split into two maximums of different intensity peaks at 105 and 118° C and in some cases the higher temperature peak had shoulders, as shown in Figure 7. Thermal history was excluded as the cause for double melting peaks since the same thermograms were obtained in the second heating run. The appearance of double peaks in most anti-corrosion films and even multiple processes in some samples stems from the differences in branching of the corresponding LDPE [10] (olefine chains of different length tend to crystallize separately). The branching could not be further analyzed by FTIR because intensity of 2900 cm^{-1} absorptions was too high.

TABLE 1

The temperatures and melting heats of investigated anti-corrosion films; thermogram types are shown on Figure 7

Sample	Thermogram type	Peak 1 T / ° C	Peak 2 T / ° C	Total ΔH Jg ⁻¹
19970	g	104.7	117.2	98.1
19971	f	105.8	114.6	83.5
19980	d	105.4	118.2	96.9
19981	d	104.8	117.2	99.5
19990	d	105.2	117.1	86.8
19991	d	105.8	117.2	82.2
19992	b	104.8	116.0	79.7
20000	g	104.8	117.8	88.6
20010	d	104.1	117.0	85.4
20011	c	104.6		94.4
20020	a	107.0		87.3
20021	e	104.8	117.0	85.5
20022	a	107.0		86.6
20030	e	106.2	119.2	86.5

VCI of the Anti-Corrosion Films

PIXE spectra of all anti-corrosion films, as received, were recorded. A typical PIXE spectrum is shown in Figure 8, prominent Mo K_α peak was present in all cases and it is the most intense peak presented in all films. After the correction for background, the molybdenum peak intensity was 1–2 orders of magnitude greater than any peak of other presented elements. Such high concentrations of molybdenum imply that VCI in investigated anti-corrosion films was molybdate based.

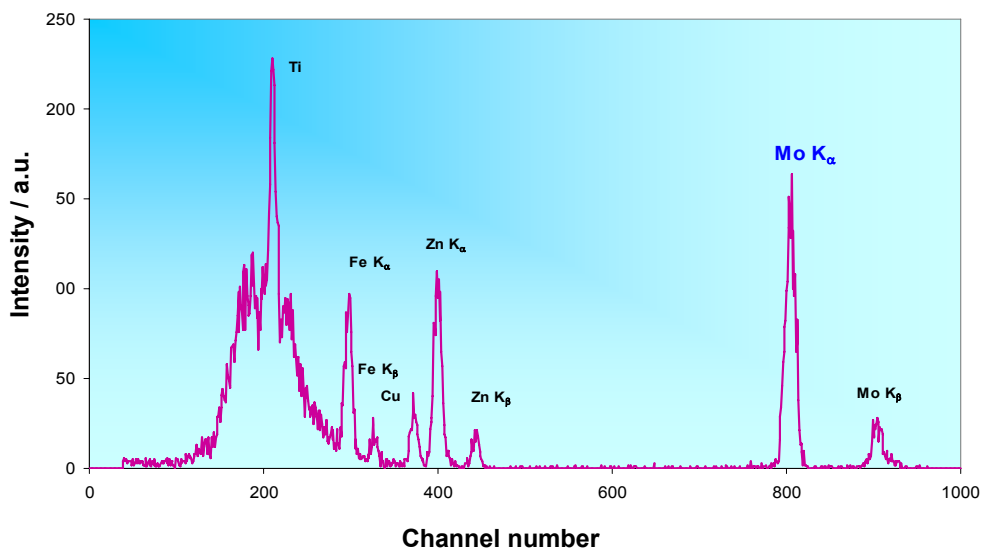


FIGURE 8 - Typical PIXE spectrum of an anti-corrosion film

Molybdate anion, MoO_4^{2-} , is often used as corrosion inhibitor that is considered to be environment-friendly. It is classified as an anodic inhibitor without oxidizing properties, because of that oxygen has to be presented for molybdate to provide corrosion inhibition. The mechanism of its anti-corrosion activity includes adsorption on the metal surface and incorporation into pre-existing oxide film. Based on temperature dependence of inhibition process, El Din and Wang [11] concluded that formation of bond is questionable. There is no data on initial molybdate content of VCI in analyzed polymer films and its lowest concentration needed to provide anti-corrosion protection is also unknown. If the molybdate concentration in investigated polymer films was high enough, its characteristic absorptions at 915 and 460 cm^{-1} should be detected in FTIR spectra of the anti-corrosive films. As can be seen in Figure 2 no such absorptions were detected so only highly sensitive PIXE spectroscopy could provide the information on concentration of molybdenum without introducing additional errors.

From the intensity of the Mo K_α the concentration of molybdenum in films was calculated as a measure of molybdate based VCI content in the anti-corrosion films. The concentrations of Mo plotted against the time passed from the beginning of use of each film are shown in Figure 9.

The plot revealed that analyzed anti-corrosion films can be divided into three groups according to the molybdenum concentration. The highest concentration was in group A films implying the highest initial concentration of VCI. Its concentration decreased with time faster than that of group B anti-corrosion films that had intermediate molybdenum concentration. In the group C are the films with lowest concentration of molybdenum that is apparently constant over time. No influence of LDPE structure (Figure 7 and Table 1) on the rate of the VCI content decrease is seen for analyzed samples. The division of samples into groups and corresponding concentrations of Mo is listed in Table 2.

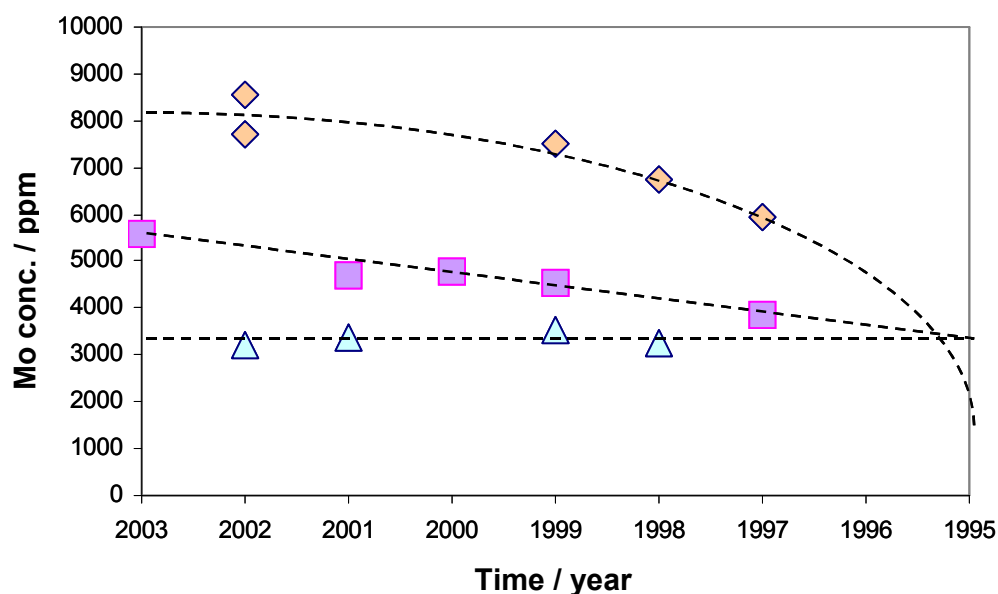


FIGURE 9 - The concentrations of molybdenum in analyzed anti-corrosion films of different age

TABLE 2
Three groups of anti-corrosion films differing in concentrations of molybdenum and in the rate of Mo concentration decrease

Year	A		B		C	
	Sample	Mo conc. ppm	Sample	Mo conc. ppm	Sample	Mo conc. ppm
1997	19970	5935	19971	3875		
1998	19981	6734			19980	3245
1999	19992	7522	19990	4542	19991	3553
2000			20000	4788		
2001			20011	4693	20010	3367
2002	20020	8534				
2002	20021	715			20022	3220
2003			20030	5571		

In a group with the lowest molybdenum concentration the VCI content has obviously decreased to saturation level for the polyethylene film under ambient conditions. No further emission of VCI could be expected from films in group C and, consequently, no anti-corrosion protection could be expected of such films. Accordingly, the time at which concentration of VCI reaches 4000 ppm of Mo is set as end of life for the anti-corrosion polymer film. The concentration of molybdenum in anti-corrosion films of group A tends to reach that level in about 8 years, 7 years for films of group B. The lasting of anti-corrosion protection by protective layer formed during the period in which molybdate was emitted out of the anticorrosion polymer film is not known and should also be investigated.

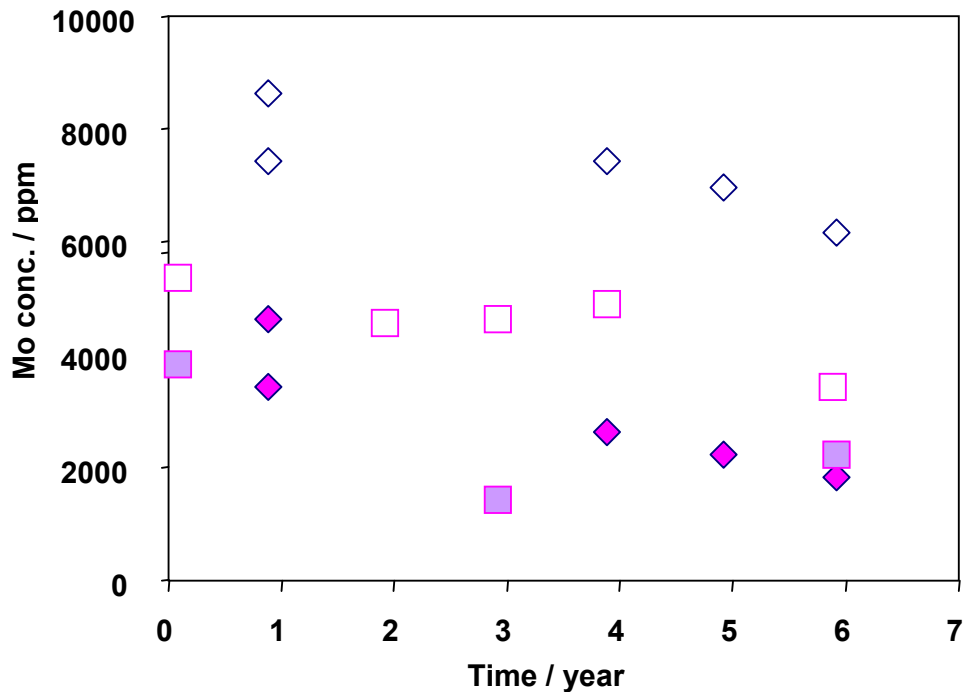


FIGURE 10 - The concentrations of molybdenum in selected anti-corrosion films of different age as received (white signs) and after accelerated aging (grey signs)

Anti-corrosion polymer films that showed molybdenum concentration decrease over time, i.e. those of group A and most of group B, were subjected to the accelerated aging in vacuum at 50° C. The aging temperature had to be below the start of the melting process because it could influence the diffusion of VCI and has been determined to begin at 60° C. After 223 days of the accelerated aging PIXE spectroscopic determination of molybdenum content was repeated (Figure 10). A significant decrease in molybdenum concentration occurred, more prominent for group A, confirming the evaporation of molybdate VCI out of the LDPE film. The differences between films of group A and group B were preserved after aging, justifying the previous division of the samples into the groups. It should be noted that the final concentrations of Mo in aged films in most cases fell much below 4000 ppm what is a consequence of vacuum application during aging so it is not possible to correlate the length of time of the accelerated aging with aging under ambient conditions.

Conclusions

PIXE analysis of characteristic X-rays revealed that VCI in the investigated anticorrosion film samples of different age was molybdate based. The anti-corrosive polymer films can be divided into three groups that substantially differ in molybdate concentration and in the rate of its evaporation. Evaporation of molybdate based VCI and the division of films into groups was confirmed by repeated PIXE determination after accelerated aging.

When the concentration of molybdenum in polymer films falls below 4000 ppm, no emission of VCI can be expected under ambient conditions. For the anti-corrosion polymer films that showed molybdenum concentration decrease with time, it was estimated that significant VCI emission lasts up to 6 or 7 years, depending on the initial concentration of VCI.

Minimum concentration of molybdate based VCI in anti-corrosion polymer that is capable of formation of protective film on metal surface and how long that film, covered by the polymer no longer emitting VCI, remains on metal surface has to be determined.

Acknowledgements

The authors are grateful to Mrs. Zorica Veksli, PhD, Mrs. Dunja Čukman, PhD, and Mr. Krešimir Kvastek, PhD, for discussions and their very useful suggestions.

References

1. Mišković L, Madžar T, Vignetti AM, Wuertz BL, Rogan I (2005) Mater Perform 44: 44
2. Estevaso LRM, Nascimento RSV (2005) Corrosion Sci 43: 1133
3. Spemann D, Deltschew R, Lorenz M, Butz T (2004) Nucl Instrum Methods Phys Res Sect B-Beam Interact Mater Atoms 219–220: 693
4. Leewis CM, Simons DPL, de Jong AM, Broer DJ, de Voigt MJA (2000) Nucl Instrum Methods Phys Res Sect B-Beam Interact Mater Atoms 161: 651
5. Leewis CM, Mutsaers PHA, de Jong AM, van IJzendoorn LJ, Broer DJ, de Voigt MJA (2001) Nucl Instrum Methods Phys Res Sect B-Beam Interact Mater Atoms 181: 367
6. Tadić T, Jakić M, Medunić Z, Quartarone E, Mustarelli P (2001) Nucl Instrum Methods Phys Res Sect B-Beam Interact Mater Atoms 181: 404
7. Moretto GL, Markwitz A, Hall SB, Burrell AK, Officer DL, Campbell WM, Collis GE (2001) Mod Phys Lett B 15: 1411
8. Hummel DO (1978) Atlas der Polymer- und Kunststoffanalyse, Bd. 1, Carl Hanser Verlag, Muenchen
9. Kaiserberger E, Moehler H (1991) Netzsch Annual for Science and Industry, Vol 1.,Wuertzburg Selb
10. Shanks RA, Amarasinghe G (2000) Polymer 41: 4579
11. El Din AMS, Wang LF (1996) Desalination 107: 29